


Company Address	SGL Group - The Carbon Company, Werner-von-Siemens-Str. 18, 86405 Meitingen, Germany
Gasket Type	Sigraflex Universal V20010C2I
Sealing element dimensions [mm]	92 x 49 x 2


L [mg/(s*m)]	Q _{min/L} [MPa]	Minimum stress to seal Q _{min/L} (at assembly), Q _{Smin/L} (after off-loading) for p = 10 bar									
		Q _{Smin/L} [MPa]									
		Q _A = 10 MPa	Q _A = 20 MPa	Q _A = 30 MPa	Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa	Q _A = 100 MPa	Q _A = 120 MPa	Q _A = 140 MPa	Q _A = 160 MPa
10 ⁰	5	5	5	5	5	5	5	5			5
10 ⁻¹	5	5	5	5	5	5	5	5			5
10 ⁻²	18		10	5	5	5	5	5			5
10 ⁻³	48					22	7	5			5
10 ⁻⁴	94							67			8
10 ⁻⁵	139										67
10 ⁻⁶											
10 ⁻⁷											
10 ⁻⁸											

Leakage - ambient temperature / inner pressure = 10 bar

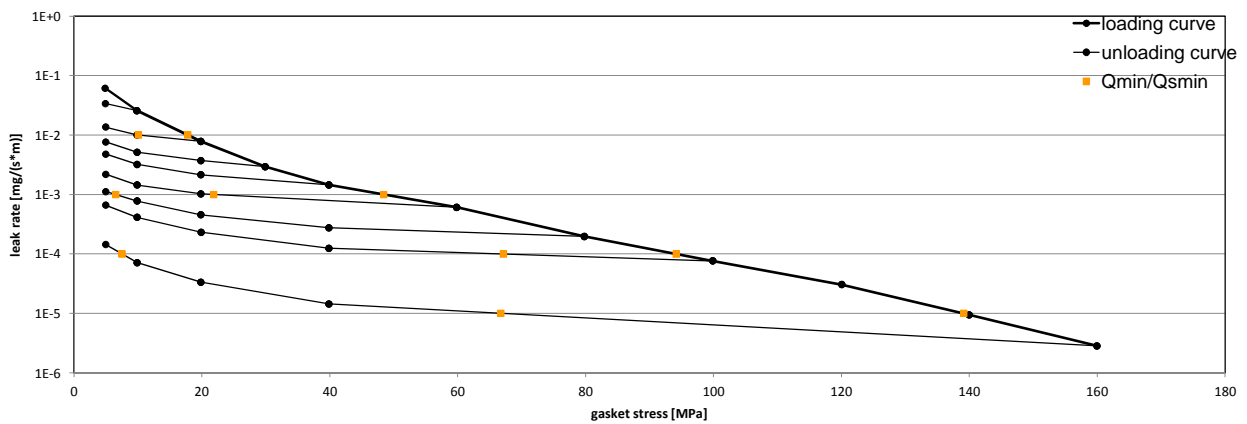

L [mg/(s*m)]	Q _{min/L} [MPa]	Minimum stress to seal Q _{min/L} (at assembly), Q _{Smin/L} (after off-loading) for p = 40 bar									
		Q _{Smin/L} [MPa]									
		Q _A = 10 MPa	Q _A = 20 MPa	Q _A = 30 MPa	Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa	Q _A = 100 MPa	Q _A = 120 MPa	Q _A = 140 MPa	Q _A = 160 MPa
10 ⁰	5	5	5	5	5	5	5	5			5
10 ⁻¹	17		9	5	5	5	5	5			5
10 ⁻²	39				38	10	5	5			5
10 ⁻³	81							28			6
10 ⁻⁴	127										30
10 ⁻⁵											
10 ⁻⁶											
10 ⁻⁷											
10 ⁻⁸											

Leakage - ambient temperature / inner pressure = 40 bar

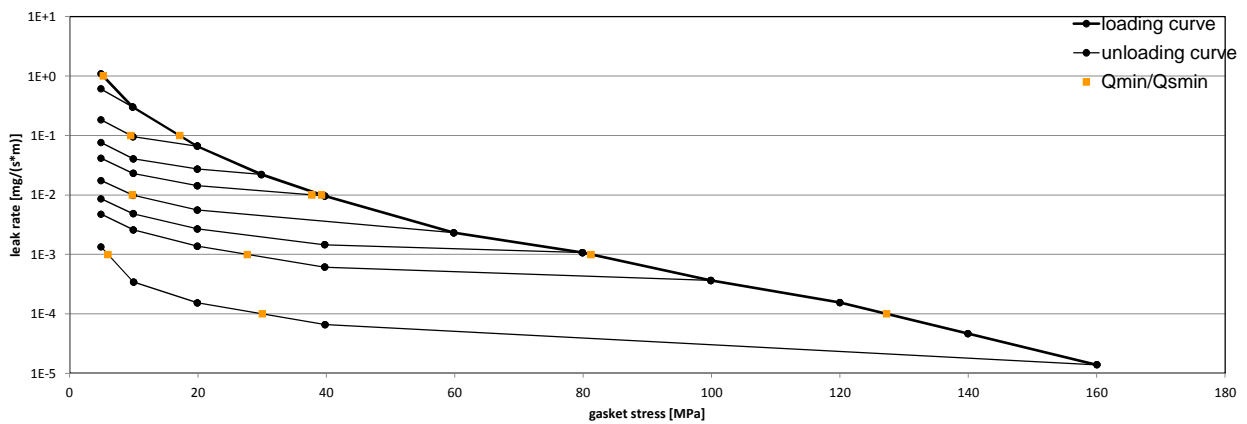

Note: the content of darkened cells was not determined respectively is unnecessary

Rev - No: 2

Creation date of this sheet:

17.02.2014

page 1 of 2



Center of Sealing Technologies, Bürgerkamp 3, 48565 Steinfurt, Germany

