


Company Address	SGL Group - The Carbon Company, Werner-von-Siemens-Str. 18, 86405 Meitingen, Germany
Gasket Type	Sigraflex Economy V20010C4
Sealing element dimensions [mm]	92 x 49 x 2


L [mg/(s*m)]	Q _{min/L} [MPa]	Minimum stress to seal Q _{min/L} (at assembly), Q _{Smin/L} (after off-loading) for p = 10 bar									
		Q _{Smin/L} [MPa]									
		Q _A = 10 MPa	Q _A = 20 MPa	Q _A = 30 MPa	Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa	Q _A = 100 MPa	Q _A = 120 MPa	Q _A = 140 MPa	Q _A = 160 MPa
10 ⁰	5	5	5	5	5	5	5	5			5
10 ⁻¹	5	5	5	5	5	5	5	5			5
10 ⁻²	21			11	5	5	5	5			5
10 ⁻³	81							49			15
10 ⁻⁴	132										85
10 ⁻⁵											
10 ⁻⁶											
10 ⁻⁷											
10 ⁻⁸											

Leakage - ambient temperature / inner pressure = 10 bar

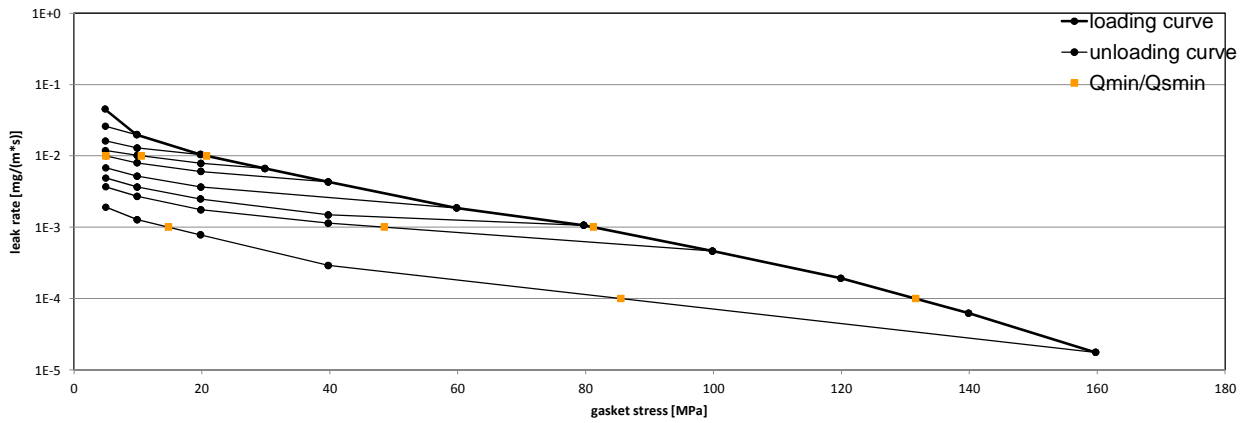

L [mg/(s*m)]	Q _{min/L} [MPa]	Minimum stress to seal Q _{min/L} (at assembly), Q _{Smin/L} (after off-loading) for p = 40 bar									
		Q _{Smin/L} [MPa]									
		Q _A = 10 MPa	Q _A = 20 MPa	Q _A = 30 MPa	Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa	Q _A = 100 MPa	Q _A = 120 MPa	Q _A = 140 MPa	Q _A = 160 MPa
10 ⁰	5	5	5	5	5	5	5	5			5
10 ⁻¹	13		6	5	5	5	5	5			5
10 ⁻²	55					48	23	14			5
10 ⁻³	106										37
10 ⁻⁴	145										122
10 ⁻⁵											
10 ⁻⁶											
10 ⁻⁷											
10 ⁻⁸											

Leakage - ambient temperature / inner pressure = 40 bar

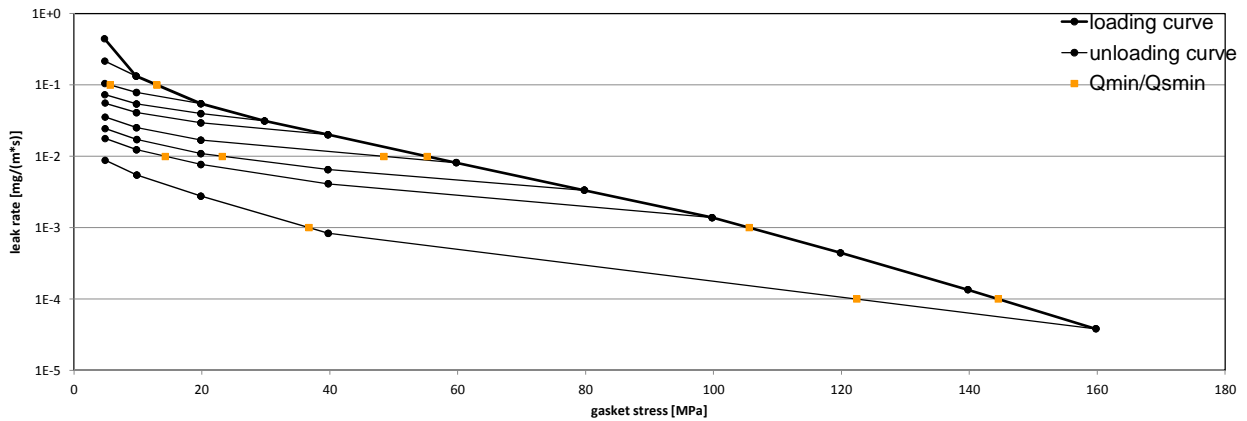

Note: the content of darkened cells was not determined respectively is unnecessary

Rev - No: 1

Creation date of this sheet:

18.10.2011

page 1 of 2



Center of Sealing Technologies, Bürgerkamp 3, 48565 Steinfurt, Germany

