



Company Address	Gambit-Lubawka Sp. z o.o., ul. Wojska Polskiego 16, 58-420 Lubawka, Poland	According to DIN EN 13555 2014-07
Gasket Type	Gamprofil GR	
Sealing element dimensions [mm]	69 x 53 x 5.5	

L [mg/(s*m)]	Q _{min/L} [MPa]	Minimum stress to seal Q _{min/L} (at assembly), Q _{Smin/L} (after off-loading) for p = 40 bar									
		Q _{Smin/L} [MPa]									
		Q _A = 10 MPa	Q _A = 20 MPa	Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa	Q _A = 100 MPa	Q _A = 120 MPa	Q _A = 140 MPa	Q _A = 160 MPa	
10 ⁰	6	6	6	6	6	6	6			6	
10 ⁻¹	16		6	6	6	6	6			6	
10 ⁻²	35			21	10	7	6			8	
10 ⁻³	67					37	23			10	
10 ⁻⁴	96						84			17	
10 ⁻⁵	126									41	
10 ⁻⁶	153									137	

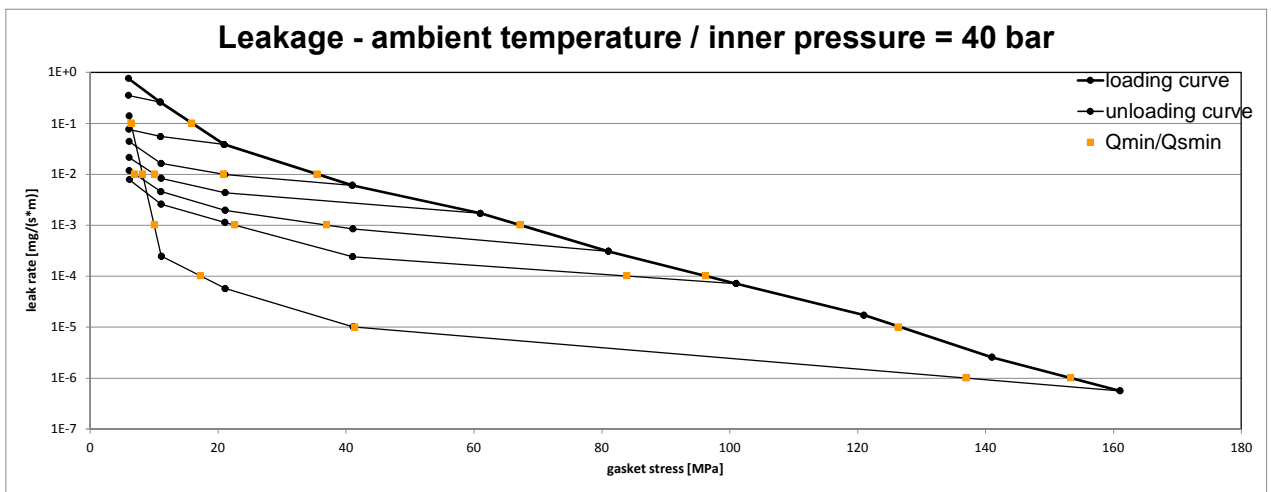

L [mg/(s*m)]	Q _{min/L} [MPa]	Minimum stress to seal Q _{min/L} (at assembly), Q _{Smin/L} (after off-loading) for p = 80 bar							
		Q _{Smin/L} [MPa]							
		Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa	Q _A = 100 MPa	Q _A = 120 MPa	Q _A = 140 MPa	Q _A = 160 MPa	
10 ⁰	21	21	21	21	21			21	
10 ⁻¹	29	11	21	13	21			21	
10 ⁻²	56		45	19	21			21	
10 ⁻³	82				25			21	
10 ⁻⁴	99				89			12	
10 ⁻⁵	122							38	
10 ⁻⁶	152							141	

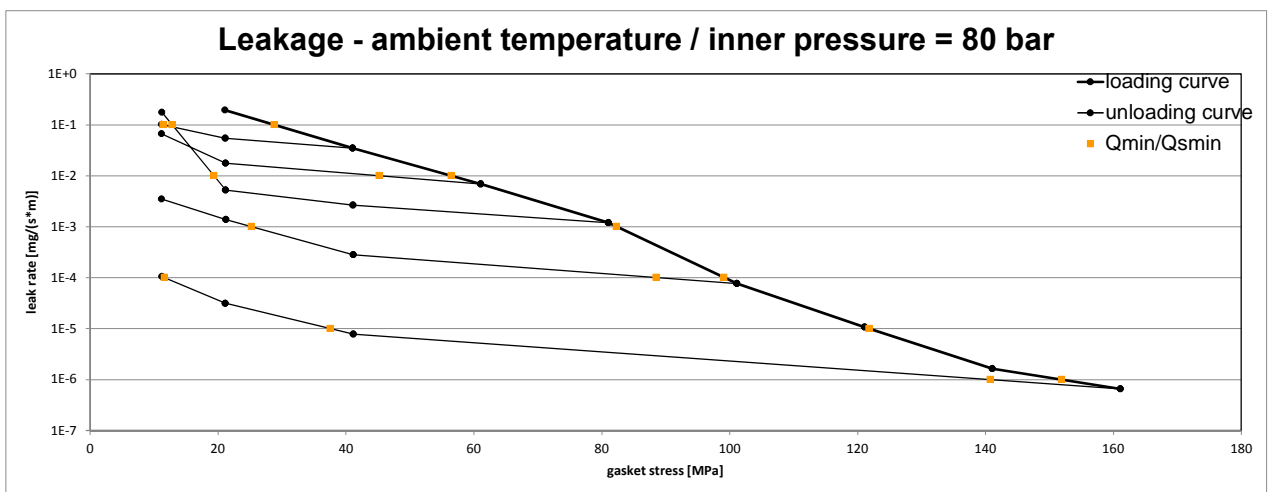

Note: the content of darkened cells was not determined respectively is unnecessary Rev - No: 1 Creation date of this sheet: 2015-11-05

